

1-1-2014

## Experimental investigation of mixtures of bentonite and dredged sediments from Chorfa dam in Algeria

ZEHOOR LABIOD - ALOUI

HABIB TROUZINE

MOULAY SMAINE GHEMBAZA

TAHAR NOUIOUA

YAHYA SEBAIBI

Follow this and additional works at: <https://journals.tubitak.gov.tr/earth>



Part of the [Earth Sciences Commons](#)

---

### Recommended Citation

ALOU, ZEHOOR LABIOD -; TROUZINE, HABIB; GHEMBAZA, MOULAY SMAINE; NOUIOUA, TAHAR; and SEBAIBI, YAHYA (2014) "Experimental investigation of mixtures of bentonite and dredged sediments from Chorfa dam in Algeria," *Turkish Journal of Earth Sciences*: Vol. 23: No. 3, Article 7. <https://doi.org/10.3906/yer-1302-13>

Available at: <https://journals.tubitak.gov.tr/earth/vol23/iss3/7>

This Article is brought to you for free and open access by TÜBİTAK Academic Journals. It has been accepted for inclusion in Turkish Journal of Earth Sciences by an authorized editor of TÜBİTAK Academic Journals. For more information, please contact [academic.publications@tubitak.gov.tr](mailto:academic.publications@tubitak.gov.tr).

## Experimental investigation of mixtures of bentonite and dredged sediments from Chorfa dam in Algeria

Zehour LABIOD-ALOUI, Habib TROUZINE\*, Moulay Smaïne GHEMBAZA, Tahar NOUIOUA, Yahya SEBAIBI

Civil Engineering and Environmental Laboratory (LGCE), Faculty of Technology, Sidi Bel Abbes University, Sidi Bel Abbes, Algeria

Received: 28.02.2013 • Accepted: 26.11.2013 • Published Online: 21.03.2014 • Printed: 18.04.2014

**Abstract:** Geotechnical properties of dredged sediment from Chorfa dam in Algeria and their mixtures (5%, 10%, 15%, 20%, and 25%) with bentonite were investigated through a series of laboratory experimental tests in order to investigate possibilities of their usage as a barrier against the spread out of the Sebkhia of Oran in the northwest of Algeria. Grain size and Atterberg limits tests, chemical and mineral analyses, and compaction, vertical swelling, and horizontal and vertical permeability tests were performed on the soils and their mixtures using tap water and the salty Sebkhia water. The results indicate that the bentonite specimens remolded and inundated with Sebkhia salty water have less swell potential than those prepared with tap water. The addition of bentonite to Chorfa sediment increases the density, limit liquid, specific surface, and swell potential of the mixtures. Compaction tests show a decrease in the optimum moisture and an increase in maximum dry densities as the bentonite content increases. The horizontal and vertical permeabilities decrease relatively with the addition of bentonite.

**Key words:** Dredged sediment, bentonite, salty water, barrier

### 1. Introduction

The world's reservoirs are currently filling with sediments at a rate of approximately 1% per year (World Commission on Dams, 2000; De Vente et al., 2005). This implies that within about 50 years, the world's water storage in reservoirs will be half of the current storage, which will have large economic and environmental consequences, especially in semiarid environments where many reservoirs have been built for water supply, irrigation, flood control, and production of electricity. This sediment storage can also have large implications for ecosystem and coastal development downstream of large river systems (World Commission on Dams, 2000; De Vente et al., 2005). Sediment dredging is a lake-restoration technique that removes the surface sediment layer rich in pollutants in order to decrease their release from the sediments to the water column (Semcha, 2006). Dredging is currently the most commonly selected option for remedying contaminated sediments (Gustavson et al., 2008).

The management of dredged material has become an environmental and economic concern for a large number of countries since international and European laws have become more stringent (Marot, 1998; Samara et al., 2009). Various alternatives to the disposal of the processed material, such as sea deposit, landfilling, and treatment processes, have been investigated. The effect of disposal in open-water has been

widely studied (Krieger and Barber, 1970; Rosenberg, 1977; Samara et al., 2009). Landfilling requires large spaces and long-term monitoring; however, it is less accepted by public opinion (Samara et al., 2009). On the other hand, treatment processes reduce the toxicity and volume of dredged material, but in comparison with open-water and upland disposal, the treatment cost is not yet competitive enough (Rosenberg, 1977; Samara et al., 2009; Tribout and Husson, 2011; Zri et al., 2011). This underlines the necessity to find ecological valorization paths for processed material to make these alternatives economically competitive (Samara et al., 2009).

The Sebkhia of Oran (northwestern Algeria), which is 56.870 ha at 35°22'N, 000°48'W, is a large endorheic depression of tectonic origin with a seasonal saline lake and flats characterized by halophilic vegetation and periodic flooding (Khaznadar et al., 2009).

This work aimed to examine the possibility of using a mixture confected with dredged sediment of Chorfa dam and bentonite as a barrier in the proximity of the airport of Oran (Algeria) in order to stop the spread of the Sebkhia. Chorfa sediment, bentonite, and Sebkhia water were analyzed, and then mixtures were confected. Compaction, vertical swelling, and horizontal and vertical permeability tests were done using Sebkhia and tap water.

\* Correspondence: h.trouzine@gmail.com

**2. Experimental investigation**

**2.1. Materials used**


Two soils of different origins and physical properties were used to achieve the clay barrier. Samples were obtained from dredged sediment of the Chorfa dam (northwestern Algeria). The used bentonite was manufactured by the Bental factory in Maghnia (northwestern Algeria).

Both soils were subjected to several laboratory identification tests using standard procedures adopted by the French standard. The results are shown in Table 1.

**2.1.1. Chorfa sediment**

Chorfa specimens are river sediments, generally cohesive brown and gray soils; their major clay minerals are calcite, quartz, and a small amount of kaolinite. The grain-size distribution and chemical composition of these soils are given in Figure 1. Their engineering and chemical properties are summarized in Tables 1 and 2, respectively. The chemical analysis of Chorfa sediment and bentonite was carried out in accordance with NF EN 1744 (AFNOR, 2010) and the results are presented in Table 2. The main constituents of Chorfa sediment are silica (as SiO<sub>2</sub>), calcium oxide (as CaO), aluminum (as Al<sub>2</sub>O<sub>3</sub>), and iron oxide (as Fe<sub>2</sub>O<sub>3</sub>). The total amount of SiO<sub>2</sub>, CaO, Al<sub>2</sub>O<sub>3</sub>, and Fe<sub>2</sub>O<sub>3</sub> is 78.7%, which is less than the determined value for bentonite (89.55%).

Sediments can absorb various chemicals contained in industrial and domestic wastewaters and can be polluted. Run-off water often contains many chemical constituents, including heavy metals (e.g., Cd, Cr, Cu, Fe, Pb, As, and Zn), organometallic species, polycyclic aromatic hydrocarbons, fossil fuels (petrol and diesel), lubricating and transmission oils, grease, and anticorrosion and antifreeze agents (Ward, 1995). The Chorfa sediment seems to be unpolluted.

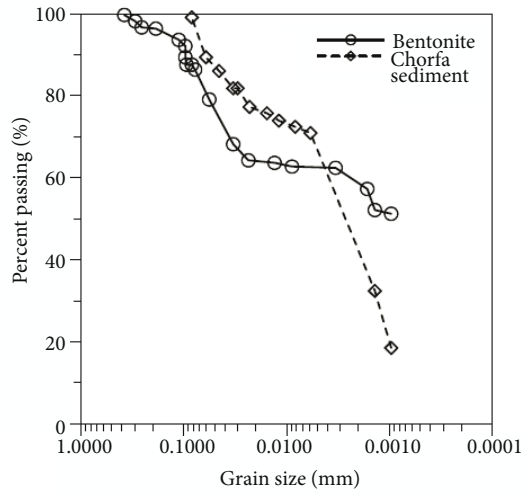

about 7.3% for Chorfa sediments samples. The loss on ignition, at 750 °C, is about 16.39%. The chemical method gives a value of 4.4% of organic matter for Chorfa sediment and 2.5% for bentonite. The specific gravity, obtained using a pycnometer (NF P94-054; AFNOR, 1991), is about 2.67. The maximal and minimal void ratios were calculated theoretically using solid constituent and dry unit weight according to  $e = \frac{\gamma_s}{\gamma_d} - 1$ . The void ratio values range between 1.03 and 2.02.

Specific surface area of the sediment was determined with methylene blue test (NF P94-068; AFNOR, 1998a). The specific area is about 147 m<sup>2</sup>/g, and the volume of methylene blue is about 7 cm<sup>3</sup>. The soil is compacted with standard Proctor energy (NF P94-093; AFNOR, 1999); the optimum moisture content is about 25%, which greater than the determined value for the bentonite (32%). The maximum dry density of Chorfa sediment is about 1.36.

**2.1.2. Bentonite**

The grain-size distribution of the bentonite is shown in Figure 1. Its chemical and index properties are summarized in Tables 1 and 2, respectively. The main constituent of the bentonite is silica at 65.2%; the SiO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> ratio equals 3.78. The clay is dominant (Table 2) at 85%, and the plasticity index of the bentonite is 93%, which is 3 times the plasticity index of the Chorfa sediments. The specific area is about 462 m<sup>2</sup>/g, and the bentonite contains a high percentage of clay. According to the USCS, the bentonite of Maghnia is defined as clay with high plasticity (CH) (Trouzine et al., 2012).

**2.1.3. Sebkha water**

All tests were performed using salty Sebkha water, which is, according to the World Health Organization, far from drinkable (Table 3).

**2.2. Mixture designs**

Geotechnical barriers are often constructed with bentonite. The high cost of bentonite led to the idea of mixing

bentonite with sediment. The Chorfa sediment sample and bentonite were dried in an oven at approximately 105 °C before grinding. They were then blended to prepare mixtures under dry conditions. The mixture design of the Chorfa sediment and bentonite was based on dry weight percentages of total mixture. The amounts of bentonite were chosen to be 5%, 10%, 15%, and 25% by dry weight of mixtures. The mixture design is given in Table 4.

In many research studies, mixtures are prepared at optimum Proctor water content or at a content corresponding to the limit liquid. In the present study, the sediment–bentonite mixtures were mixed with the required amount of water according to the optimum Proctor moisture content. All mixing was done manually and proper care was taken to prepare homogeneous mixtures at each stage.

The Chorfa sediment and bentonite mixtures were compacted at their optimum water contents. The compaction processes were performed by standard Proctor tests in accordance with NF P94-093. Compacted samples were used for permeability and swelling tests.

**2.3. Compaction tests**

The mixture compaction parameters, such as the maximum dry unit weight and the optimum moisture content, were obtained by standard Proctor tests in accordance with NF P94-093. To determine the compaction parameters, Chorfa sediment–bentonite mixtures were blended with various amounts of water. Each material was evaluated at 4 different water concentrations in 3 steps. To ensure uniform compaction, the required quantities of Chorfa sediment–bentonite mixtures were placed inside mold-collar assemblies and compressed alternately in 3 steps from the 2 ends until the samples were reached.

**2.4. Vertical swelling tests**

The samples of mixtures were all initially compacted at their optimum moisture content in a standard Proctor mold and extruded using a cutting ring before the one-dimensional consolidation tests. The compressibility and swelling behaviors of the Chorfa sediment–bentonite mixtures were assessed from one-dimensional consolidation tests. These samples were confined in a consolidation ring, Sebkha water was added to the samples, and they were allowed to swell freely. Other series of tests were performed using tape water for remolding and inundating bentonite specimens.

Swelling tests were performed according to AFNOR XP P94-091 (AFNOR, 1995b) on all compacted specimens. These tests were conducted in a conventional odometer, 50 mm in diameter and 20 mm thick. The following equation was used for calculation of the vertical swelling percentage:

$$G(\%) = \frac{v_f - v_i}{v_f} \cdot 100\% = \frac{h_i - h_f}{h_f} \cdot 100\% = \frac{\Delta h}{h_i} \cdot 100\% \tag{1}$$

**Table 3.** Sebkha water quality.

Minerals	World Health Organization requirements (mg/L)	Sebkha water (mg/L)
NO <sub>3</sub>	6	>5
SO <sub>4</sub>	400	>1000
Cl	500	>1000
Na	200	>600
K	20	>600
Ca		>500
Mg		>500
Ca+Mg	500	

**Table 4.** Mixture design and property.

Engineering properties	Mixture 1	Mixture 2	Mixture 3	Mixture 4
Chorfa sediment (%)	95	90	85	75
Bentonite (%)	5	10	15	25
Density (mg/m <sup>3</sup> )	2.38	2.53	2.56	2.59
Liquid limit (%)	72	73	79	81
Plastic limit (%)	41	42	43	44
Plasticity index	31	31	36	37
Methylene blue values				
Volume of blue V <sub>B</sub> (cm <sup>3</sup> )	6.6	7.3	8.3	10
Specific surface SST (m <sup>2</sup> /g)	138.6	153.3	174.3	210
Optimum moisture content (%)	28	27	25	25
Maximum dry density	1.37	1.38	1.39	1.40

where  $V_i$  is the initial volume of the soil,  $V_f$  is the final volume of the soil,  $h_i$  is the initial height of the soil, and  $h_f$  is the final height of the soil.

## 2.5. Permeability tests

### 2.5.1. Vertical permeability

Vertical permeability was first measured using compaction permeameter (mold with the same dimension of standard Proctor mold). Specimens were first prepared with Sebkha water at the normal optimum Proctor energy then compacted in 3 layers in a standard Proctor mold using dynamic compaction (NF P94-093). The upper and lower plates of the Proctor mold were replaced by compaction permeameter ones in order to allow the flow of water through the compacted sample. The compacted specimens were first saturated for a period of about 1.5 to 2 months. Full sample saturation was confirmed by water coming out of the water outlet portal of the compaction permeameter equipment. Coefficient of permeability ( $k$ ) values were calculated as follow:

$$k = \frac{a.L}{A(t_1 - t_2)} \cdot \ln \left( \frac{h_1}{h_2} \right) \quad (2)$$

where  $a$  is the inner cross-section of the standpipe,  $L$  is the length of the specimen,  $A$  is the cross-sectional area of the compacted soil specimen,  $h_1$  is the head at time  $t_1$ , and  $h_2$  is the head at time  $t_2$ .

### 2.5.2. Horizontal permeability

The flow of water through a porous medium is governed by Darcy's law: if we consider a cylindrical tube with section  $S$ , and this cylindrical tube is filled with a porous material over length  $L$ , which is circulated water over a total height  $\Delta H$  (constant) when the medium is saturated with water, then:

$$Q = k \cdot \frac{\Delta h}{l} \cdot A \quad (3)$$

where  $Q$  is the flow (m<sup>3</sup>/s),  $k$  is the permeability or hydraulic conductivity (m/s),  $A$  is the surface perpendicular to flow (m),  $l$  is the length of the sample (7 cm), and  $\Delta h$  is the level difference between upstream and downstream.

Horizontal permeability tests were done using drainage and seepage tank model HM 169, as shown in Figure 2.

## 3. Results

Basic properties of mixtures samples are summarized in Table 4. Figures 3a and 3b show, respectively, the effect of bentonite content on consistency limits of Chorfa sediment and the location of the samples of sediments, bentonite, and their mixtures on Casagrande's chart by plotting plasticity index (%) against liquid limit (%).

Figures 4a and 4b show the effects of bentonite on the optimum moisture contents and maximum dry unit weights normalized by setting these values for Chorfa sediment.


The amount of swelling of Chorfa sediment, bentonite, and their mixtures is shown in Figure 5.

Results of vertical and horizontal permeability tests of the mixtures are shown in Figure 6.

## 4. Discussion

Liquid limit, plasticity index, and specific surface area increase gradually as the bentonite is added (Table 4). This can be explained by the increase of clay content in the mixtures (Figure 3a).

The change in consistency limits of the mixtures may be due to the mixture type (Bell, 1993), the cation exchange capacity (Okagbue and Onyeobi, 1999; Sivapullaiah et al., 2000), or the relative amount of clay mineral in the mixtures (Schmitz et al., 2004). The location of mixtures

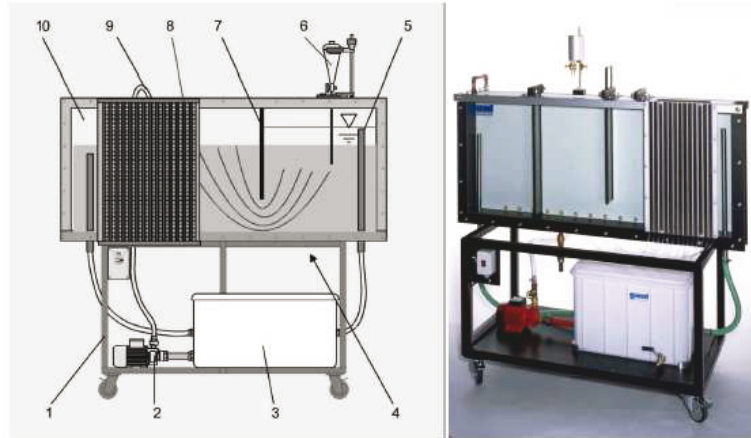

1 laboratory trolley, 2 pump, 3 supply tank, 4 measuring gland, evenly distributed over the base of the tank, 5 adjustable overflow pipe, 6 device for injecting the contrast producing medium, 7 pile planking, 8 fourteen tube manometer, 9 water feed, can be positioned as required, 10 tank with viewing window made of special glass

**Figure 2.** Drainage and seepage tank.


on Casagrande’s plasticity chart is given in Figure 3b. The main aim is to determine whether fine soil is silt or clay. Clay plots are present above the A-line and silt below. Generally, high liquid limit values correlate with high plasticity. Silts and organic soils have a low plasticity index compared to their liquid limit. Clay soils have a high plasticity index in relation to their liquid limit. Clay minerals have the capacity to take in moisture and still retain some cohesion (USCS). According to Casagrande’s chart, Chorfa sediment and their mixtures are classified as OH (organic soil of high plasticity) or MH (silt of high plasticity), whereas bentonite is classified as CH (clay of high plasticity).

Casagrande (1948) suggested that the effect of increasing the organic content of a soil is to increase the liquid limit with no appreciable change in the plasticity index, thus causing the soil to shift below the A-line. Holtz and Krizek (1970) suggested an increase of the plasticity index with the increase in the liquid limit for materials with increasing amounts of organic content.

The optimum moisture content of Chorfa sediment–bentonite mixtures decreased with the addition of bentonite contents (Figure 4a). However, it was observed that the maximum dry unit weights of Chorfa sediment–bentonite mixtures increased for the same compaction effort (Figure 4b). Bentonite changed the particle size distribution and surface area of the composite samples. Decreases in the optimum moisture contents are due to the change in surface area of composite samples. In the same way, the reason for the increase in the maximum dry unit weights of the mixtures is the addition of higher amounts of bentonite, which filled the voids of the composite samples. Holtz and Krizek (1970) studied such soils and found that the maximum dry density of compaction decreased with

increasing organic content, whereas the optimum moisture content increased with increasing organic content. Similar behavior was also observed by Schmidt (1965).

Interestingly, Jesmani et al. (2008) studied the variation of  $\gamma_{dmax}$  and  $\omega_{opt}$  versus the clay content with various compaction energy levels. Study of the  $\gamma_{dmax}$  vs. clay (%) curve shows that, at all compaction energy levels, the curve ascends with a steep slope to a certain percentage of clay and then descends to hold a mild slope. On the other hand, there is an optimum percentage of clay for different energy levels at which  $\gamma_{dmax}$  is obtained. At low energy levels the effect of optimum clay value is more outstanding, but at high energy levels this effect is less considerable. At low energy levels, the present clay content of the mixture fills out the pores between the coarse particles and, thus, at the

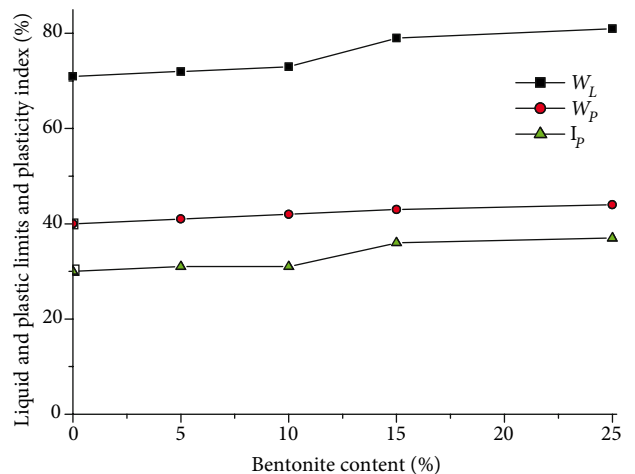

**Figure 3a.** Effect of bentonite content on consistency limits of Chorfa sediment.



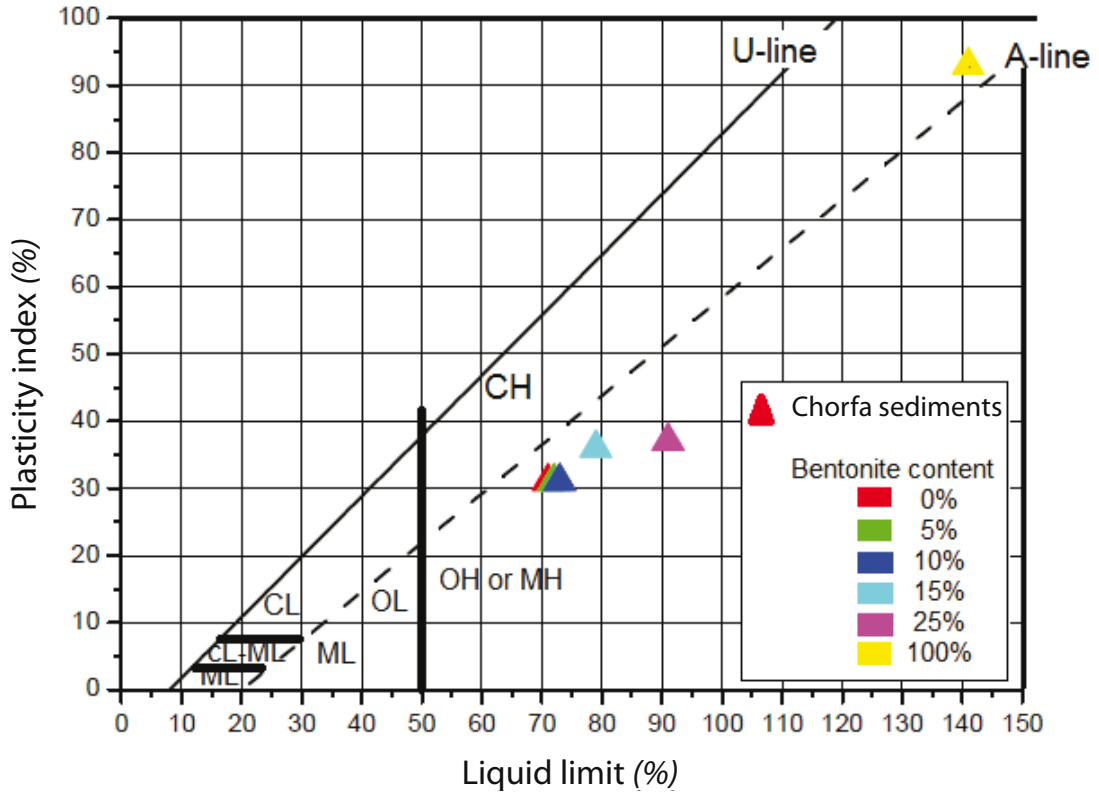


Figure 3b. Location of studied samples on Casagrande's plasticity chart.

outset, increasing the clay content results in an increasing  $\gamma_{dmax}$ . Passing over an optimum clay content, the repulsive effect between the layers of clay prevents optimum compaction. More increase in fine grains causes the coarse

grains to be away from each other; this changes the soil state from semibuoyant to buoyant and, as a result,  $\gamma_{dmax}$  decreases (Jesmani et al., 2008).

At high energy levels, the effect of this optimum clay content is less considerable. It seems that the high compaction energies have a more important effect on obtaining higher maximum dry unit weight. The optimum water content keeps a rising trend due to the increase in clay content of the mixtures (Jesmani et al., 2008).

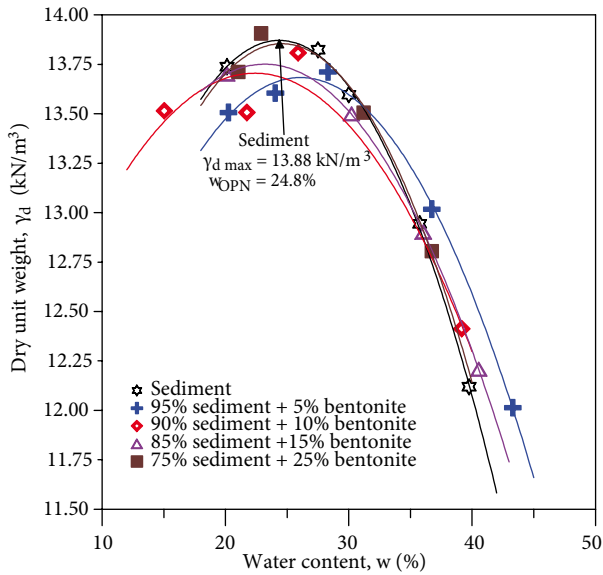


Figure 4a. Compaction characteristics of Chorfa sediment and their mixtures.


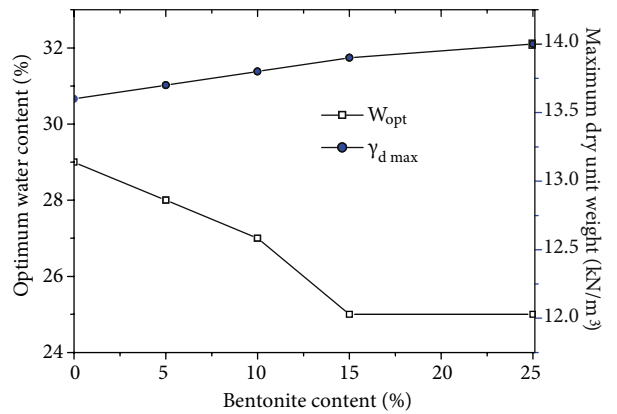


Figure 4b. Effect of bentonite on the compaction characteristics of Chorfa sediment.

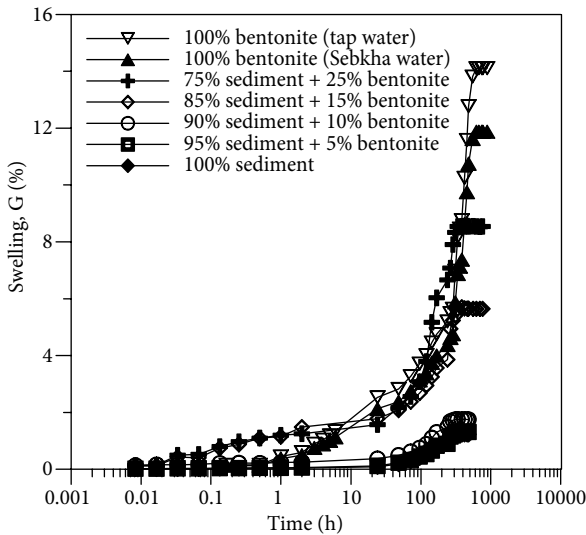


**Figure 5.** Swell potential of bentonite, Chorfa sediment, and their mixtures.

The mechanism of swelling is complex and is influenced by a number of factors, such as the type and amount of clay minerals present in the soil, the specific surface area of the clay, the structure of the soil, and the valence of the exchangeable cation and mixture type (Bell, 1993; Okagbue and Onyeobi, 1999; Sivapullaiah et al., 2000; Schmitz et al., 2004; Trouzine et al., 2012).

The maximum swelling of bentonite specimens (using tap water) was about 14% (Figure 5). Interestingly for specimens remolded and inundated with Sebkha salty water, the maximum swelling was only 12%; this could be due to the direction of salt diffusion during dissipation of osmotic suction difference, which has a significant bearing on the swelling behavior of unsaturated expansive clays (Rao and Thyagaraj, 2007). Swelling rapidly goes beyond 70% in 1 h and then 90% in 24 h, and then the evolution of swelling becomes very slow and stabilization begins to occur from the fourth day. The vertical swelling percentages of Chorfa sediment–bentonite mixture samples increased from 6% to 9%. It can be seen that the bentonite increased the vertical swelling of Chorfa sediment–bentonite mixtures.

The bentonite improved the permeability values of samples containing bentonite. The permeability values steadily decreased with increasing bentonite content and low values were finally reached in the composite samples containing 25% bentonite contents (Figure 6). The decrease in the permeability values was due to the decreasing void ratio of the samples containing bentonite. The vertical permeability coefficient ranges from  $1.005 \times 10^{-10}$  to  $8.89 \times 10^{-11}$ , and it increases with the percentage of bentonite added to the mixture (Figure 6). For a landfill

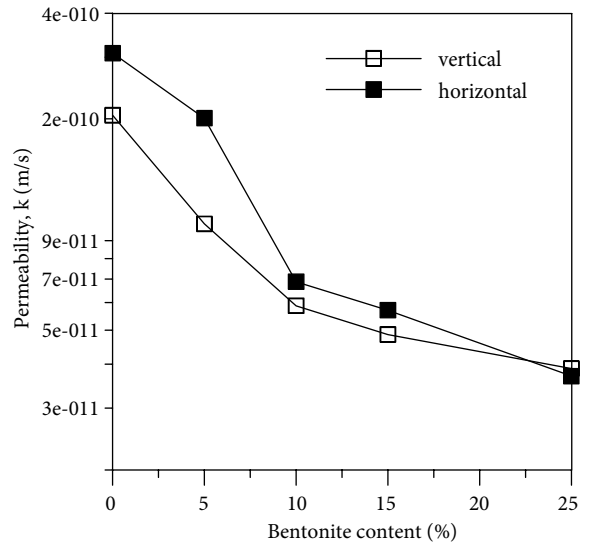

**Figure 6.** Effect of bentonite content on vertical and horizontal permeability of Chorfa sediment.

site, the vertical permeability coefficient is required to be less than  $10^{-9}$  (Ait Saidi, 2003).

The decrease in the permeability values was due to the decreasing void ratio of the samples containing bentonite.

The horizontal permeability values steadily decreased with increasing bentonite content and low values were finally reached in the composite samples containing 25% bentonite contents (Figure 6). For the composite samples containing 25% bentonite contents, the horizontal permeability is constant.

The following conclusions on the effect of bentonite content on the geotechnical and hydraulic characteristics for the Chorfa sediment that was investigated in this study were drawn:

- Geotechnical characteristics vary depending on the bentonite content: the liquid limit, the plasticity index, and specific surface increase with the increase of bentonite content.

- The bentonite content changed the compaction parameters of Chorfa sediment. The optimum moisture content values decreased with the addition of bentonite contents and the maximum dry unit weight values increased with increased bentonite contents.

- The bentonite content increased the swelling behavior of Chorfa sediment–bentonite mixture samples; however, the salty medium is likely to diminish the percentage of swelling.

- The bentonite content decreased the vertical permeability of Chorfa sediment–bentonite mixtures.

- As for the horizontal permeability, the bentonite content decreased the horizontal permeability of Chorfa sediment–bentonite mixtures.



- The organic matter contained in Chorfa sediment decreases when mixed with bentonite, thus making the mixture more efficient.

- The additive mixtures played an important role in improving the problem of permeability of the Chorfa sediment. These results demonstrate the possibility of using the dredged Chorfa sediment treated with bentonite as a geotechnical barrier to stop the spread of the Sebkha. This geotechnical barrier may be strengthened, in terms of permeability, by decreasing the bentonite content.

## Nomenclature

Basic SI units are given in parentheses.

$a$	Cross-sectional area of the standpipe (m <sup>2</sup> )
$A$	Cross-sectional area of the specimen (m <sup>2</sup> )
$e$	Void ratio (dimensionless)
$G$	Vertical swelling percentage (dimensionless)
$h_i, h_f$	Initial and final height of soil (m)

$h_1, h_2$	Head (m)
$I_p$	Plasticity index (dimensionless)
$k$	Permeability or hydraulic conductivity (m/s)
$l$	Length of sample (m)
$L$	Length of the specimen (m)
$Q$	Flow (m <sup>3</sup> /s)
$SST$	Specific surface (m <sup>2</sup> /kg)
$t_1, t_2$	Time (s)
$VB$	Volume of blue (m <sup>3</sup> )
$V_i$	Initial volume of soil (m <sup>3</sup> )
$V_f$	Final volume of soil (m <sup>3</sup> )
$W_{OPN}$	Optimum Water Content (dimensionless)
$W_L$	Liquid limit (dimensionless)
$W_P$	Plastic limit (dimensionless)
$\gamma_d$	Dry unit weight (N/m <sup>3</sup> )
$\gamma_{dmax}$	Maximum dry unit weight (N/m <sup>3</sup> )
$\gamma_s$	Unit weight of solid constituent (N/m <sup>3</sup> )

## References

- AFNOR (1991). NF P94-054, Sols: reconnaissances et essais, Détermination de la masse volumique des particules solides des sols, méthode de pycnomètre à eau. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1992). NF P94-057, Sols: reconnaissances et essais, Analyse granulométrique des sols, Méthode par sédimentation. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1995a). NF P94-051, Sols: reconnaissance et essais, Détermination des limites d'Atterberg, Partie 1 : Limite de liquidité, Méthode du cône de pénétration. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1995b). XP P94-091, Sols: reconnaissances et essais, Essai de gonflement à l'odomètre. Détermination des déformations par chargement de plusieurs éprouvettes. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1996). NF P94-056, Sols: reconnaissances et essais, Analyse granulométrique, Méthode de tamisage à sec après lavage. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1998a). NF P94-068, Sols: Reconnaissance et essais, Mesure de la capacité d'adsorption de bleu de méthylène d'un sol ou d'un matériau rocheux, Détermination de la valeur de bleu de méthylène d'un sol ou d'un matériau rocheux par l'essai à la tache. Paris, France: Association Française de Normalisation (in French).
- AFNOR (1998b). XP P94-047, Sols: Reconnaissance et essais - Détermination de la teneur pondérale en matière organique - Méthode par calcination Paris, France: Association Française de Normalisation (in French).
- AFNOR (1999). NF P94-093, Sols: reconnaissances et essais, Détermination de référence de compactage d'un matériau, Essai Proctor normal - Essai Proctor modifié. Paris, France: Association Française de Normalisation (in French).
- AFNOR (2010). NF EN 1744, Essais visant à déterminer les propriétés chimiques des granulats. Paris, France: Association Française de Normalisation (in French).
- Ait Saadi L (2003). Méthodologie de contrôle de l'homogénéité et de la perméabilité des barrières argileuses. PhD, Institut National des Sciences Appliquées de Lyon, France (in French).
- Bell FG (1993). Engineering Treatment of Soils. London, UK: E. & F.N. Spon.
- Casagrande A (1948). Classification and identification of soils. Transactions ASCE 113: 901-930.
- De Vente J, Poesen J, Verstraeten G (2005). The application of semi-quantitative methods and reservoir sedimentation rates for the prediction of basin sediment yield in Spain. J Hydrol 305: 63-86.
- Gustavson K, Burton GA, Francingues NR, Reible D, Vorhees DJ, Wolfe JR (2008). Evaluating the effectiveness of contaminated-sediment dredging. Environ Sci Technol 42: 5042-5047.
- Holtz RD, Krizek RJ (1970). Properties of slightly organic topsoils. J Construct Div-ASCE 96: 29-43.
- Jesmani M, Manesh AN, Hoseini S M R (2008). Optimum water content and maximum dry unit weight of clayey gravels at different compactive efforts. EJGE 13: 1-14.
- Khaznadar M, Vogiatzakis IN, Griffiths GH (2009). Land degradation and vegetation distribution in Chott El Beida wetland, Algeria. J Arid Environ 73: 369-377.

- Krieger Y, Barber RT (1970). Effects of waste dumping in New York bight on the growth of natural populations of phytoplankton. *Environ Pollut* 5: 237–252.
- Marot F (1998). Caractérisation et traitement de sédiments de dragage contenant des polluants métalliques. Orleans, France: BRGM (in French).
- Okagbue CO, Onyeobi T (1999). Potential of marble dust to stabilize red tropical soils for road construction. *Eng Geol* 53: 371–380.
- Rao SM, Thyagaraj T (2007). Role of direction of salt migration on the swelling behaviour of compacted clays. *Appl Clay Sci* 38: 113–129.
- Rosenberg R (1977). Effects of dredging operations on estuarine benthic macrofauna. *Mar Pollut Bull* 8: 102–104.
- Samara M, Lafhaj Z, Chapiseau C (2009). Valorization of stabilized river sediments in fired clay bricks: factory scale experiment. *J Hazard Mater* 163: 701–710.
- Schmidt NO (1965). A study of the isolation of organic matter as a variable affecting engineering properties of soil. PhD, University of Illinois at Urbana, USA.
- Schmitz RM, Schreoder C, Charlier R (2004). Chemo-mechanical interactions in clay: a correlation between clay mineralogy and Atterberg limits. *Appl Clay Sci* 26: 351–358.
- Semcha A (2006). Valorisation des sédiments de dragage : Applications dans le BTP, cas du barrage de Fergoug. PhD, Reims Champagne-Ardenne University, France (in French).
- Sivapullaiyah PV, Sridharan A, Bhaskar RKV (2000). Role of amount and type of clay in the lime stabilization of soils. *Ground Improvement* 4: 37–45.
- Tribout C, Husson B (2011). Use of treated sediments in road building techniques. *Eur J Env Civil Eng* 15: 197–213.
- Trouzine H, Bekhiti M, Asroun A (2012). Effects of scrap tyre rubber fibre on swelling behavior of two clayey soils in Algeria. *Geosynth Int* 19: 124–132.
- Ward NI (1995). Trace elements. In: Fifield FW, Haines PJ, editors. *Environmental Analytical Chemistry*. Glasgow, UK: Blackie Academic, pp. 320–351.
- World Commission on Dams (2000). *Dams and Development: A New Framework for Decision-Making*. London, UK: Earthscan Publications Ltd.
- Zri A, Abriak NE, Zentar R (2011). Caractérisation physico-mécanique d'un sédiment brut et traité à la chaux. *Eur J Env Civil Eng* 15: 239–267 (in French).