

1-1-2022

## Detailed structure analyses on Cobalt doped PbTiO<sub>3</sub> powders

EBRU ERÜNAL

Follow this and additional works at: <https://journals.tubitak.gov.tr/chem>

 Part of the [Chemistry Commons](#)

---

### Recommended Citation

ERÜNAL, EBRU (2022) "Detailed structure analyses on Cobalt doped PbTiO<sub>3</sub> powders," *Turkish Journal of Chemistry*. Vol. 46: No. 4, Article 21. <https://doi.org/10.55730/1300-0527.3425>

Available at: <https://journals.tubitak.gov.tr/chem/vol46/iss4/21>

This Article is brought to you for free and open access by TÜBİTAK Academic Journals. It has been accepted for inclusion in Turkish Journal of Chemistry by an authorized editor of TÜBİTAK Academic Journals. For more information, please contact [academic.publications@tubitak.gov.tr](mailto:academic.publications@tubitak.gov.tr).

## Detailed structure analyses on Cobalt doped PbTiO<sub>3</sub> powders

Ebru ERÜNAL\* 

Department of Chemical Engineering, Çukurova University, Adana, Turkey

Received: 22.09.2021 • Accepted/Published Online: 08.04.2022 • Final Version: 05.08.2022

**Abstract:** The identification of the defects and secondary phases which significantly affect the material properties are of crucial importance. In this study, a systematic structure examination of PbTiO<sub>3</sub> and cobalt doped PbTiO<sub>3</sub> powder ceramics was carried out. X-ray diffraction (XRD), Fourier-transform infrared (FT-IR), Raman, and electron paramagnetic resonance (EPR) spectroscopies were applied along with nonsimultaneous thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC). The doped and undoped PbTiO<sub>3</sub> materials were synthesized via a practical sol-gel route that takes place at 50 °C. The perovskite formation for both materials was verified. The dislocation density of cobalt doped PbTiO<sub>3</sub> was found to be 0.0121 nm<sup>-2</sup> while it was 0.00239 nm<sup>-2</sup> for the undoped material. Besides, a strong strain effect was observed for cobalt doped PbTiO<sub>3</sub> via XRD. This was attributed to the Co<sub>3</sub>O<sub>4</sub> phase which was detected through EPR and FT-IR analyses. The formation of the Co<sub>3</sub>O<sub>4</sub> phase during synthesis revealed the previously unexpected nonimproved ferroelectric behavior for cobalt doped PbTiO<sub>3</sub>. The dielectric constant and the dielectric loss (tan δ) of cobalt doped PbTiO<sub>3</sub> were estimated as 1066 and 0.8370, respectively.

**Key words:** Co<sub>3</sub>O<sub>4</sub>, Doping, sol-gel synthesis, perovskite, PbTiO<sub>3</sub>

### 1. Introduction

Today lead-based ferroelectric materials are still preferred in the industry due to their superior properties when compared with their alternatives [1–5]. Recently, there are even studies on the implementation of the spontaneous electric polarization of PbTiO<sub>3</sub> ceramics for photocatalytic applications to be used for the spatial separation of photogenerated electrons and holes [6,7]. In this context, the effect of doping should be well determined and carefully analyzed.

In general, the off-centered Ti<sup>4+</sup> ions within the oxygen octahedra and other oxygen vacancies as a result of doping are attributed to the enhanced material properties [8]. One common mistake is the expected site of the dopant ion to be founded in such an ABO<sub>3</sub> type perovskite without considering its effective ionic radius. As a rule of thumb, ions with similar or closer effective ionic radii are more likely to change place with each other [9]. Therefore, if an ion is intended to dope on A site but has a closer effective ionic radius to the ion on B site, then there will be an excess of B site ions due to the wrong stoichiometric assumption. This will cause the formation of secondary phases. Moreover, synthesis routes would also end up with unwanted secondary phases which deteriorate the material properties instead of enhancement [10]. For example, cobalt doped PbTiO<sub>3</sub> would be expected to show distinct properties due to the magnetic character of the cobalt ion. However, Kumar et al. [11] reported no improvement in the ferroelectric properties of the cobalt doped PbTiO<sub>3</sub> which were obtained via sol-gel synthesis. The experimental observations are still not adequate to understand the reason for this phenomenon-whether result of secondary phases or changes in defect chemistry-. This study aimed to go further analysis of cobalt doped PbTiO<sub>3</sub> ceramics to enlighten the relation between the dielectric properties, the defects, and secondary phases obtained via sol-gel synthesis. In order to track the defect structure and secondary phases systematically, a comparative examination was carried out with the undoped PbTiO<sub>3</sub>. When the effective ionic radius of dopant ion Co<sup>2+</sup> (0.745 Å) is considered, it is expected to change place with Ti<sup>4+</sup> ion whose effective ionic radius was reported as 0.605 Å [12]. For this reason, the precursor amounts were adjusted to obtain Pb(Ti<sub>0.95</sub>Co<sub>0.05</sub>)O<sub>3</sub>. The magnetic properties and the dielectric loss constant were interpreted with the detailed characterization results obtained through X-ray diffraction (XRD), Fourier transformation infrared (FT-IR) spectroscopy, Raman spectroscopy, thermal analyses, and electron paramagnetic resonance (EPR) spectroscopy.

\* Correspondence: eerunal@cu.edu.tr

## 2. Experimental

### 2.1. Materials

Lead(II) acetate trihydrate (extra pure, Merck), titanium isopropoxide (98%, Acros Organics), cobalt(II) nitrate hexahydrate (Carlo Erba), ethanol (absolute analytic, Merck), glacial acetic acid (Merck), and citric acid (%99, Sigma Aldrich) were used to obtain the undoped and cobalt doped  $\text{PbTiO}_3$ .

### 2.2. Sol-gel synthesis


The synthesis was carried out according to the method given by Odabasi [13]. Lead(II) acetate trihydrate ( $\text{Pb}(\text{CH}_3\text{COO})_2 \cdot 3\text{H}_2\text{O}$ ) was dissolved in glacial acetic acid at room temperature. Appropriate dopant precursor ( $\text{Co}(\text{II}) (\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ ) was also dissolved in this mixture. In another beaker, titanium isopropoxide ( $\text{Ti}(\text{OCH}(\text{CH}_3)_2)_4$ ) was added to a mixture of glacial acetic acid and ethanol via a syringe. Two solutions were stirred at room temperature for around one h and then mixed. Vigorous stirring continued until a clear solution formed. Then, a mixture of citric acid and methanol was added to this solution. After a homogenous mixture was obtained, the temperature was raised up to  $50^\circ\text{C}$  and heated for about one h. The cobalt doped material turned pink while the undoped material was off-white. All materials were calcined in two steps: Firstly, overnight at  $100^\circ\text{C}$  and then at  $650^\circ\text{C}$  for around three h with a heating rate of  $50^\circ\text{C}/\text{min}$ .

## 3. Results and discussion

### 3.1. XRD analysis

The crystal structure was characterized with a Rigaku Miniflex XRD instrument (with a  $\text{CuK}\alpha$ ,  $\lambda = 0.154 \text{ nm}$ ) between  $20$ – $80^\circ$ . XRD patterns of both materials are given in Figure 1. The Miller indices of the main reflection planes (hkl) for  $\text{PbTiO}_3$  perovskite structure are shown according to JCPDS card no. 01-077-2002. The perovskite structure with a tetragonal symmetry was obtained for both doped and undoped materials [14,15]. However, both homogenous and inhomogeneous strain effects are observed for the cobalt doped  $\text{PbTiO}_3$ . The slight shifts from peak positions for (001), (002), (201), (112) planes point out homogenous strain while the broadened peaks at  $22$ – $23^\circ$ ,  $32$ – $33^\circ$ ,  $53^\circ$ , and  $56^\circ$  show inhomogeneous strain. A similar inhomogeneous strain pattern was recorded by Elbasset et al. [16] for cobalt doped  $\text{PbTiO}_3$  and interpreted as either grain size or local disorder effect. On contrary, the formation of a monoclinic  $\text{PbTi}_3\text{O}_7$  phase (JCPDS card no. 00-021-0949), which was observed for the undoped  $\text{PbTiO}_3$  around  $28.9^\circ$  and  $34.6^\circ$ , vanished upon cobalt doping [17,18]. Hence, the formation of this phase was also mentioned by Lee et al. [18] for  $\text{PbTiO}_3$  powders synthesized via a similar sol-gel synthesis route. It was recorded that the formation of  $\text{PbTi}_3\text{O}_7$  phase could be eliminated via calcination temperatures above  $600^\circ\text{C}$  for more than three h.

The average crystallite sizes were estimated -with the help of Scherrer equation using (101) base peak- as  $34.2 \text{ nm}$  and  $17.6 \text{ nm}$  for undoped and cobalt doped  $\text{PbTiO}_3$ , respectively. The formation of defects as a result of cobalt doping may decrease the lattice parameters [19]. The lattice parameters were exploited from JPCDS Card Numbers via HighScore Plus software and compared with the calculated lattice parameters in Table. The difference between the expected (according to JCPDS Card Number) and calculated lattice parameters would result in phase transition temperature shifts like  $\pm 5^\circ\text{C}$  from Curie temperatures [10].

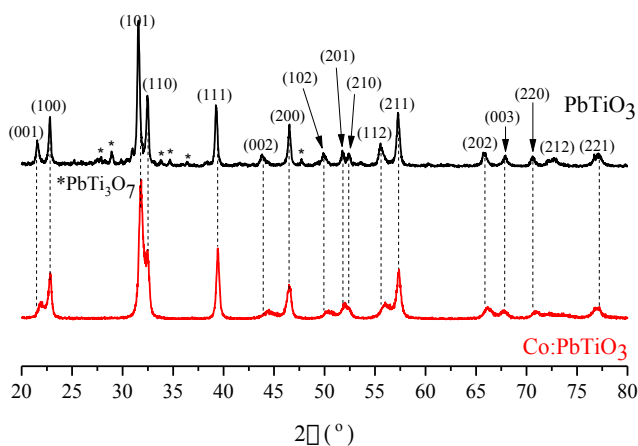

**Figure 1.** XRD patterns of  $\text{PbTiO}_3$  (black line) and cobalt doped (red line)  $\text{PbTiO}_3$  (red line)  $\text{PbTiO}_3$

**Table.** Estimated lattice parameters for tetragonal symmetry.

Material	Lattice parameters (Å)				
	Database search			Calculated	
	JCPDS card number	a = b	c	a = b	c
PbTiO <sub>3</sub>	01-077-2002	3.9000	4.1500	3.8953	4.1312
Co:PbTiO <sub>3</sub>	01-078-0299	3.9400	4.0630	3.9005	4.0679

The dislocation densities were found as  $2.39 \times 10^{-3} \text{ nm}^{-2}$  and  $1.21 \times 10^{-2} \text{ nm}^{-2}$  for the undoped and cobalt doped PbTiO<sub>3</sub> with the help of the Williamson-Hall formula [20]. The very low dislocation density of the undoped PbTiO<sub>3</sub> is consistent with the similarly calculated lattice parameters. Moreover, the porosity of cobalt doped material was estimated. Bulk density ( $\rho_b$ ) and X-ray density ( $\rho_x$ ) were calculated as 4.504 g/cm<sup>3</sup> and 5.692 g/cm<sup>3</sup> according to the method given by Kumar et al. [11]. The porosity percentage (P%) was evaluated as 20% according to the following formula  $P\% = [1 - (\rho_b / \rho_x)] \times 100$ .

### 3.2. Thermal analysis

Thermal analyses were carried out with a Mettler Toledo instrument under N<sub>2</sub> atmosphere with a flow rate of 40 mL/min. The thermogravimetric analyses (TGA) were carried out between 25 and 900 °C with a heating rate of 10 °C/min. The detailed TGA of cobalt doped PbTiO<sub>3</sub> was shown in Figure 2(a). In general, ceramics are quite stable at high temperatures [10]. As expected, the weight loss percentages were insignificant: 0.6% for undoped and 0.3% for cobalt doped PbTiO<sub>3</sub>, as shown in Figure 2(a). It was already reported that PbTiO<sub>3</sub> ceramics decompose at temperatures higher than 900 °C [10]. Hence, PbO<sub>x</sub> phases are decomposing between the measured temperature ranges [21]. The relatively higher weight loss of undoped PbTiO<sub>3</sub> was attributed to the decomposition of the PbO<sub>2</sub> phase to PbO with the help of the first derivative of thermogravimetric (DTG) data as demonstrated in Figure 2(b). Hence, the uncalcined secondary phases like PbO<sub>2</sub> start to decompose around between 250–350 °C and as temperature increases, PbO phase forms. For cobalt doped sample, even though PbO<sub>2</sub> was not detected, other PbO<sub>x</sub> phases were identified [21]. Again, the decomposition of these phases ended up with PbO formation. The PbO<sub>x</sub>-related secondary phases cause the formation of cation and oxygen defects even if they are in minor amounts since they affect the ratio of Pb/Ti ion stoichiometry slightly.

The differential scanning calorimetry (DSC) measurements were conducted between 25 and 550 °C with a heating rate of 8 °C/min again under N<sub>2</sub> atmosphere. The Curie temperature at which the tetragonal crystal structure changes to the cubic phase is expected at 490 °C for PbTiO<sub>3</sub> [10]. However, the detected Curie temperature was around 480 °C for the undoped PbTiO<sub>3</sub> in Figure 3. A difference of 10 °C from the expected Curie temperature value was attributed to a lead deficient ( $V_{Pb}''$ ) PbTiO<sub>3</sub> material [22]. The formation of PbO<sub>x</sub> containing secondary phases would end up with such cation deficiencies within the perovskite structure. This will also cause the formation of oxygen vacancies ( $V_O^\bullet$ ) in order to balance the crystal charge compensation [21,23]. By this way two negatively charged holes created by cation vacancy should be balanced with 2 plus charged oxygen vacancy as shown in Eqn (1) where  $\emptyset$  corresponds to the defect-free crystal structure.



Apart from the undoped PbTiO<sub>3</sub>, the Curie temperature vanishes for the cobalt doped PbTiO<sub>3</sub> in Figure 3. This phenomenon was also reported by Odabasi [13]. It might be related to the dislocation density that was estimated through the XRD analysis. The higher dislocation density may cause a decrease in detection limits for similar phase changes in the DSC analyses. Obviously, a counter exothermic peak at the expected Curie temperature is hindered as a result of cobalt doping. In order to resolve the spectrum, modulated DSC with a much slower heating rate should be applied [24]. Moreover, a bump between 150 and 250 °C followed by a sharp transition temperature around 305 °C was detected for the cobalt doped material. A similar trend at different temperatures was also observed for the undoped material. The bump of undoped and cobalt doped PbTiO<sub>3</sub> can be seen between 220 and 320 °C. The possible reason may be a Pb including secondary phase. The PbTi<sub>3</sub>O<sub>7</sub> phase which was detected via XRD is known to be stable at these temperatures and decompose around 700 °C [18]. Another possibility is the pyrochlore (Pb<sub>2</sub>Ti<sub>2</sub>O<sub>6</sub>) phase which was mentioned by Lee et al. [18]. Even though the XRD patterns of Pb<sub>2</sub>Ti<sub>2</sub>O<sub>6</sub> were hard to detect around 30°, in the DSC analysis, the sharp peaks at 315, 305, and 257 °C clearly point out the transformation of the pyrochlore phase to the tetragonal PbTiO<sub>3</sub> [18]. Because cobalt ion was also incorporated into this pyrochlore phase, a slight shift in the observed temperature was observed for cobalt doped PbTiO<sub>3</sub>. Similar observations within the pyrochlore phase were reported for variously doped PbTiO<sub>3</sub> in literature [25–28].

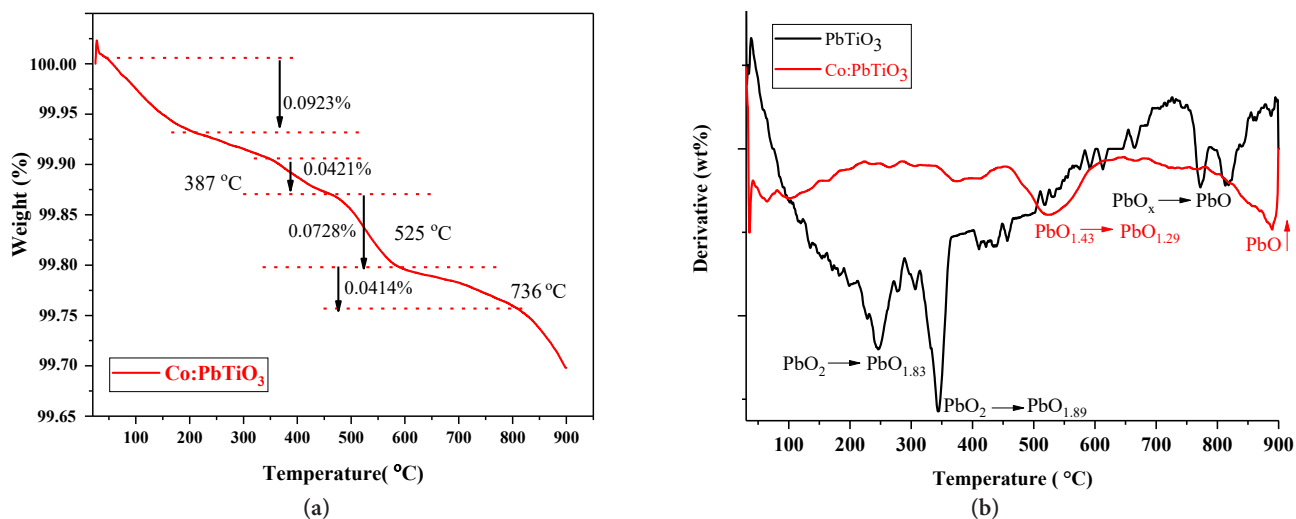


Figure 2. (a) TGA of cobalt doped  $\text{PbTiO}_3$  (b) DTG of the undoped (black line) and cobalt doped (red line)  $\text{PbTiO}_3$ .

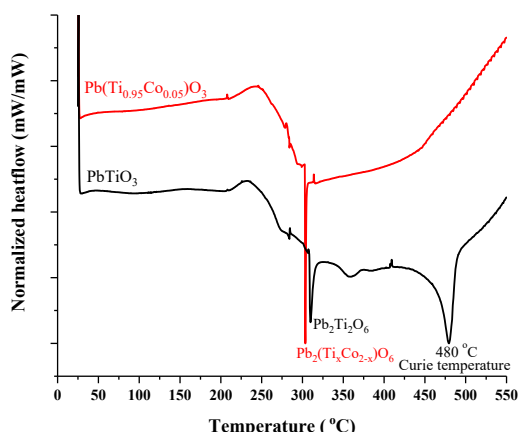


Figure 3. DSC measurements of undoped (black line) and cobalt doped (red line)  $\text{PbTiO}_3$ .

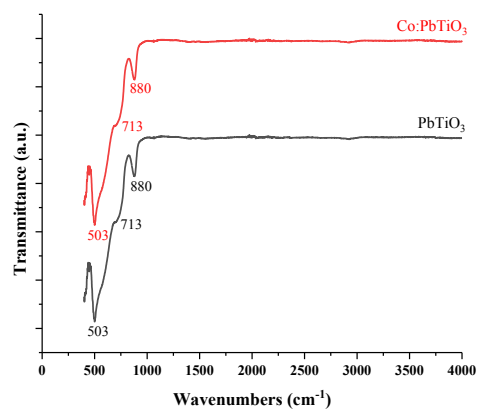


Figure 4. FT-IR spectra of undoped (black line) and cobalt doped (red line)  $\text{PbTiO}_3$ .

### 3.3 FT-IR measurements

The FT-IR measurements were conducted at room temperature, between 450 and 4000  $\text{cm}^{-1}$  via an ATR crystal Thermo Scientific instrument. Two main peaks at 503 and 880  $\text{cm}^{-1}$  for the undoped  $\text{PbTiO}_3$  are seen in Figure 4. These peaks were associated with Ti–O and Pb–O bonds, respectively [29–31]. The slight bump around 713  $\text{cm}^{-1}$ , which could also be detected for cobalt doped  $\text{PbTiO}_3$ , was attributed to six coordinated  $\text{Ti}^{4+}$  ion octahedral complexes within the perovskite structure [15]. Especially, the undoped and cobalt doped materials have quite similar spectra.

### 3.4 EPR spectroscopy

X-Band (9.7 GHz) EPR spectroscopy of doped materials was measured with a Bruker EMX 081 type EPR spectrometer at room temperature. Simply, EPR spectroscopy deals with the interaction of electromagnetic radiation with the molecule's dipole moment, which arises from an unpaired electron in its orbital [32–34]. Principally, each paramagnetic ion in a certain environment has a characteristic signal.

The  $\text{Co}^{2+}$  ion has three unpaired electrons in its high spin  $d^7$  state. The spin Hamiltonian for high spin  $\text{Co}^{2+}$  is shown in Eqn.4 where  $\beta_e$  is the Bohr magneton,  $\mathbf{B}_0$  is the applied external field,  $\mathbf{g}$  is the g-factor or g tensor,  $\mathbf{S}$  is the spin state,  $\beta_n$  is the nuclear magneton,  $\mathbf{g}_n$  is the nuclear g-factor,  $\mathbf{I}$  is the nuclear spin.  $\mathbf{A}$  is the hyperfine interaction of the nucleus with the electronic spin and  $\mathbf{D}$  is the zero-field splitting term that occurs from electron-electron dipole interaction of more than one unpaired electron containing system [33,34]. Since  $S$  is 3/2 and  $I$  is 7/2 for high spin  $\text{Co}^{2+}$  ion, splittings in its EPR spectrum are expected.

$$H = \beta_e \mathbf{B}_0 \cdot \mathbf{g} \cdot \mathbf{S} - \beta_n g_n \mathbf{B}_0 \cdot \mathbf{I} + \mathbf{S} \cdot \mathbf{D} \cdot \mathbf{S} + \mathbf{S} \cdot \mathbf{A} \cdot \mathbf{I} \quad (4)$$


Typical EPR spectrum examples for cobalt containing systems were given by Abragam & Bleaney and Telser [33,35]. Unfortunately, in Figure 5, the expected spectrum seems to vanish under the strong broad peak. A different measurement frequency rather than X Band may help to resolve this part.

In the literature, a similar broad peak was reported for  $\text{Co}_3\text{O}_4$  [36] which is obtained through the calcination of  $\text{CoO}$  between 600 and 700 °C [37]. Apparently,  $\text{CoO}$  phase was formed during sol-gel synthesis and later turned into  $\text{Co}_3\text{O}_4$  after calcination. This would result in less incorporation of  $\text{Co}^{2+}$  ions into the perovskite structure. Moreover, the broadenings in the XRD spectrum and thermal analyses of the cobalt doped material most likely arise from this complicated secondary phase. However, it should be noted that the amount of this phase must be quite low and therefore below the detection limits of XRD, since during the analyses, the spectrum related to  $\text{Co}_3\text{O}_4$  could not be exploited directly but just observed in terms of broadenings. Thus,  $\text{Co}_3\text{O}_4$  has a spinel structure where  $\text{Co}^{3+}$  ions reside in the octahedral site, while  $\text{Co}^{2+}$  ions reside in the tetrahedral sites [37,38]. Normally, bulk  $\text{Co}_3\text{O}_4$  was reported as antiferromagnetic at room temperature and  $\text{Co}_3\text{O}_4$  nanoparticles were reported as magnetic only at very low temperatures [39]. Therefore, a magnetic susceptibility measurement was carried out to verify the incorporation of  $\text{Co}^{2+}$  ions into the perovskite structure. The magnetic susceptibility was compared with a copper doped  $\text{PbTiO}_3$ , which was synthesized with a similar route [28], and shown in Figure 6. A Vibrating Sample Magnetometer (VSM) system was utilized for magnetic measurements at room temperature. Even though both materials have low magnetic behavior, when compared with copper doped  $\text{PbTiO}_3$ , cobalt doped  $\text{PbTiO}_3$  exhibits more ferromagnetic behavior. This may arise from the incorporation of cobalt ion into the  $\text{PbTiO}_3$  perovskite structure. It should be noted that  $\text{Co}^{3+}$  in the  $\text{Co}_3\text{O}_4$  phase was reported as diamagnetic due to its splitting in the spinel structure while the  $\text{Co}^{2+}$  ions have a small contribution to spin-orbit coupling. However, the magnetic susceptibility of the cobalt doped  $\text{PbTiO}_3$  material was found to be higher than  $\text{Co}_3\text{O}_4$  susceptibility as reported by Roth [38]. Therefore, this behavior was attributed to the incorporation of  $\text{Co}^{2+}$  within the targeted structure.


### 3.4. Raman spectroscopy

Raman spectroscopy was applied to verify the secondary phases detected through all other methods. It was conducted with an InVia Qontor model Renishaw instrument at room temperature. Typical  $\text{PbTiO}_3$  phonon transitions [15,39–46] can be seen in Figure 7. After doping with cobalt, most of the transitions vanished or decreased drastically. The broadening of Raman lines and larger backgrounds for bulk ceramics were interpreted as an indication of disordered or amorphous structures [40].


Moreover, secondary phase-related transitions were found for both  $\text{PbTi}_3\text{O}_7$  and  $\text{Co}_3\text{O}_4$ . For example, the modes around 129, 170, 252, 676, 749, and 836  $\text{cm}^{-1}$  were corresponding to the  $\text{PbTi}_3\text{O}_7$  phase [47], while the modes around 190, 474, 530, and 678  $\text{cm}^{-1}$  were attributed to the  $\text{Co}_3\text{O}_4$  phase [36,48].

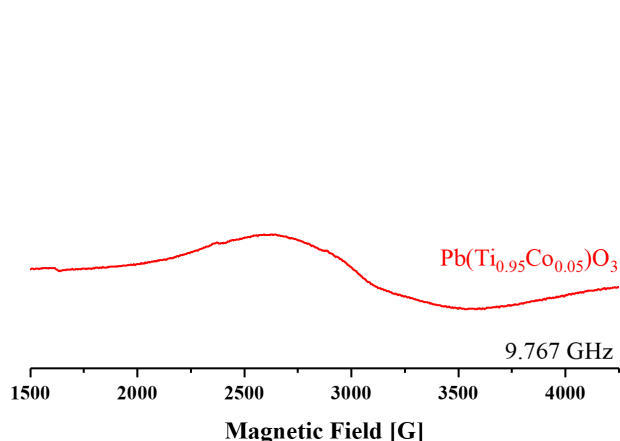

**Figure 5.** X-Band (9.767 GHz) EPR spectra of the cobalt doped  $\text{PbTiO}_3$  measured at room temperature.

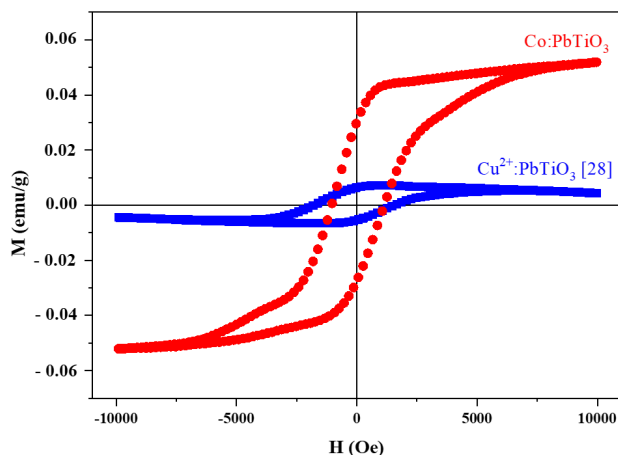

**Figure 6.** Comparison of the magnetic susceptibility measurements of cobalt (red) doped  $\text{PbTiO}_3$  and copper (blue) doped  $\text{PbTiO}_3$  [28] at room temperature.

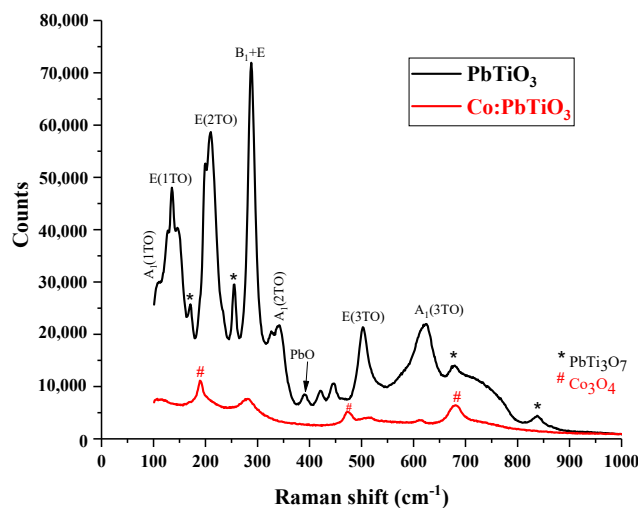

**Figure 7.** Raman spectra of undoped (black line) and cobalt doped (red line)  $\text{PbTiO}_3$ .

### 3.6. Dielectric properties

Cobalt doped  $\text{PbTiO}_3$  pellets (0.6010 cm radius and 0.771 mm thickness) were obtained under 12 MPa pressure at room temperature and sintered at 700 °C for two h. Then, the surface of the pellets was coated with gold (Au) via vapor deposition (sputtering) technique before electrical measurements. The undoped material was not dense enough to obtain a proper pellet. Capacitance (C) and dielectric loss ( $\tan \delta$ ) measurements of doped material were taken with an LCR-meter (INSTEK LCR-816) at a frequency of 1 kHz at room temperature. The capacitance (C) was measured as 1389 pF and relative permittivity (dielectric constant) was calculated as 1066. Dielectric loss ( $\tan \delta$ ) was estimated as 0.8370. The dielectric loss at 1 kHz and dielectric constant were reported as 0.09 and 96.8 for the undoped  $\text{PbTiO}_3$  capacitors [49]. The doping has affected the material's properties according to the increased values. Hence, the existence of pyrochlore phases at surfaces is known to decrease the dielectric constant. High dielectric constant value verifies the pyrochlore-free characterization results for cobalt doped material. Besides, the parameters obtained in this study are in good agreement with the literature for doped and composite  $\text{PbTiO}_3$  based ceramics [10,50,51].  $\text{Co}_3\text{O}_4$  phase seems to enhance the dielectric constant. However, the existence of  $\text{Co}_3\text{O}_4$  phase is thought to be the reason for not obtaining a proper polarization-electric field (P-E) loop hysteresis. The distorted banana shape shows a current leakage within the material. A similar P-E behavior was also observed by Kumar et al. [11]. It is obvious that the formation of CoO during sol-gel synthesis should be inhibited or this phase should be eliminated from the material before calcination so that  $\text{Co}_3\text{O}_4$  phase can be avoided to overcome this problem.

### 4. Conclusions

The structural properties of the undoped and cobalt doped  $\text{PbTiO}_3$  were investigated. Later these properties were used to interpret the nonferroelectric behavior of cobalt doped  $\text{PbTiO}_3$ .  $\text{PbO}_2$ ,  $\text{PbTi}_3\text{O}_7$ ,  $\text{Pb}_2\text{Ti}_2\text{O}_6$  were detected for the undoped  $\text{PbTiO}_3$ , while slight  $\text{PbO}_x$ ,  $\text{Pb}_2(\text{Ti}_x\text{Co}_{2-x}\text{O}_6)$  formations were observed for cobalt doped  $\text{PbTiO}_3$  through XRD, Raman and thermal analyses. Additionally,  $\text{Co}_3\text{O}_4$  phase was detected through EPR and Raman spectroscopy. The vanishing Curie temperature of cobalt doped  $\text{PbTiO}_3$  points out that a more sophisticated thermal analysis will be necessary to resolve the counter exothermic peak. The dielectric constant and dielectric loss for cobalt doped  $\text{PbTiO}_3$  were estimated in good agreement with literature as 1066 and 0.8370, respectively.

### Acknowledgments

This project is supported by Çukurova University Scientific Research Projects Coordination Unit (Project ID. FBA 2018-10647). Prof. Dr. Mustafa Polat from Hacettepe University, Prof. Dr. Ramazan Esen, and Prof. Dr. Bekir Özçelik from Çukurova University are acknowledged for their contributions to the EPR, XRD, and magnetic measurements. The Faculty of Science and Letters is acknowledged for the laboratory facilities. The author especially would like to thank Assist. Prof. Dr. Metin Özgül and Samet Abbak from Afyon Kocatepe University for dielectric and piezoelectric measurements provided. Dr. Klaus Seiffert, Oykun Gürkan, Umut Haskan, and H. Çağlar Üsdün are acknowledged for editorial assistance.

## References

- Gamboa B, Bhalla A, Guo R. Assessment of PZT (soft/hard) composites for energy harvesting. *Ferroelectrics* 2020; 555: 118-123. doi: 10.1080/00150193.2019.1691389
- Song H-C, Kang C-Y, Yoon S-J, Jeong D-Y. Engineered domain configuration and piezoelectric energy harvesting in 0.7Pb(Mg<sup>1/3</sup>Nb<sup>2/3</sup>)O<sub>3</sub>-0.3PbTiO<sub>3</sub> single crystals. *Metals and Material International* 2012; 18 (3): 499-503. doi: 10.1007/S12540-012-3018-Y
- Priya S, Myers RD. Piezoelectric energy harvester, US7649305B2, 2010.
- Hemeda OM, Eid MEA, Sharshar T, Ellabany HM, Henaish AMA. Synthesis of nanometer-sized PbZr<sub>x</sub>Ti<sub>1-x</sub>O<sub>3</sub> for gamma-ray attenuation. *Journal of Physics and Chemistry of Solids* 2021; 148: 109688. doi: 10.1016/j.jpics.2020.109688
- Eid MEA, Hemeda OM, Sharshar T, Ellabany HM, Weinstein I et al. Can nano PZT-OPC composites be used as a smart  $\gamma$ -ray attenuator? *Journal of Physics and Chemistry of Solids* 2021; 159: 110254. doi: 10.1016/j.jpics.2021.110254
- Liu Y, Ye S, Xie H, Zhu J, Shi Q et al. Internal-field-enhanced charge separation in a single-domain ferroelectric PbTiO<sub>3</sub> photocatalyst. *Advanced Materials* 2020; 32 (7): 1906513. doi: 10.1002/adma.201906513
- Zhu Q, Zhang K, Li D, Li N, Xu J et al. Polarization-enhanced photocatalytic activity in non-centrosymmetric materials based photocatalysis: A review. *Chemical Engineering Journal* 2021; 426: 131681. doi: 10.1016/j.cej.2021.131681
- Angoshtari A, Yavari A. Effect of strain and oxygen vacancies on the structure of 180° ferroelectric domain walls in PbTiO<sub>3</sub>. *Computational Material Science* 2010; 48: 258-266. doi: 10.1016/j.commatsci.2010.01.006
- Li G, Zheng L, Yin Q, Jiang B, Cao W. Microstructure and ferroelectric properties of MnO<sub>2</sub>-doped bismuth-layer (Ca, Sr)Bi<sub>4</sub>Ti<sub>4</sub>O<sub>15</sub> ceramics. *Journal of Applied Physics* 2005; 98: 064108. doi: 10.1063/1.2058174
- Jaffe B, Cook WR, Jaffe H. Piezoelectric ceramics. Academic Press, London, 1971.
- Kumar NS, Suvarna RP, Naidu KCB. Structural and ferroelectric properties of microwave heated lead cobalt titanate nanoparticles synthesized by sol-gel technique. *Journal of Materials Science: Materials in Electronics* 2018; 29: 4738-4742. doi: 10.1007/s10854-017-8429-6
- Shannon RD. Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides. *Acta Crystallographica* 1976; A32: 751-767. doi: 10.1107/S056773947600155
- Odabaşı S. Effect of cobalt doping on photocatalytic activity of lead titanate. M.Sc. Thesis, M.E.T.U., Ankara, 2018.
- Yang L, Wang Y, Wang X, Wang Y, Han G. Hydrothermal synthesis and characterization of PbTiO<sub>3</sub> microrods. *Advanced Material Research* 2011; 149: 903-906.  
doi: 10.4028/www.scientific.net/AMR.148-149.903
- Ammar MH, El-hady MM, Salama TM, Bahgat AA. Reassess study of high temperature electric transport properties of PbTiO<sub>3</sub>. *Journal of Alloys and Compounds* 2019; 770 308-319. doi: 10.1016/j.jallcom.2018.08.113
- Elbasset A, Lamcharfi T, Abdi F, Mrharrab L and Sayouri S. Effect of doping with cobalt or copper on the structure of lead titanate PT. *Indian Journal of Science and Technology* 2015; 8 (12): 1-6. doi: 10.17485/ijst/2015/v8i12/56348
- Bersani D, Lottici PP, Montenero A, Pignoni S, Gnappi G. Phase transformations in sol-gel prepared PbTiO<sub>3</sub>. *Journal of Material Science* 1996; 31: 3153-3157. doi: 10.1007/BF00354661
- Lee C-Y, Tai N-H, Sheu H-S, Chiu H-T, Hsieh SH. The formation of perovskite PbTiO<sub>3</sub> powders by sol-gel process. *Materials Chemistry and Physics* 2006; 97: 468-471. doi: 10.1016/j.matchemphys.2005.08.048
- Vinnik DA, Zherebtsov DA, Niewa R, Isaenko LI, Mikhailov GG. Distribution of dopant metals between PbTiO<sub>3</sub> crystals and PbO-B<sub>2</sub>O<sub>3</sub> flux. *Russian Journal of General Chemistry* 2014; 84: 1888-1892. doi: 10.1134/S107036321410003X
- Williamson GK, Hall WH. X-ray line broadening from filed aluminium and wolfram. *Acta Metallurgica* 1953; 1: 22-31. doi: 10.1016/0001-6160(53)90006-6
- Gavrichev K, Bolshakov A, Kondakov D, Khoroshilov A, Denisov S. Thermal transformations of lead oxides. *Journal of Thermal Analysis and Calorimetry* 2008; 92: 857-863. doi: 10.1007/s10973-007-8590-x
- Peng X, Rong Y, Fan L, Lin K, Zhu H et al. Cation deficiency effect on negative thermal expansion of ferroelectric PbTiO<sub>3</sub>. *Inorganic Chemistry Frontiers* 2015; 2: 1091-1094. doi: 10.1039/C5QI00154D
- Kröger FA, Vink HJ. Relations between the concentrations of imperfections in crystalline solids. *Solid State Physics* 1956; 3: 307-435. doi: 10.1016/S0081-1947(08)60135-6
- Höhne GWH, Hemminger WF, Flammersheim H-J. Differential scanning calorimetry, 1st ed., Springer-Verlag, Berlin, 2003.
- Lima Elton C, Araújo EB. Phase transformations in pzt thin films prepared by polymeric chemical method. *Advances in Materials Physics and Chemistry* 2012; 2: 178-184. doi: 10.4236/ampc.2012.23027



27. Kwok CK, Desu SB. Pyrochlore to perovskite phase transformation in sol-gel derived lead zirconate titanate thin films, *Applied Physics Letters* 1992; 60: 1430. doi: 10.1063/1.107312
28. Wang Y, Xu G, Yang L, Ren Z, Wei X et al. Preparation of single-crystal PbTiO<sub>3</sub> nanorods by phase transformation from Pb<sub>2</sub>Ti<sub>2</sub>O<sub>6</sub> nanorods. *Journal of Alloys and Compounds* 2009; 481: L27-L30. doi: 10.1016/j.jallcom.2009.03.073
29. Erünal E. Inhibition of secondary phase formation with minor copper doping on sol-gel derived PbTiO<sub>3</sub> powders, *Journal of Sol-Gel Science and Technology* 2021; 101: 484-492. doi: 10.1007/s10971-021-05700-0
30. 10.1007/s10971-021-05700-0
31. Chauhan AKrS, Sreenivas K. TG-DTA and FT-IR studies on sol-gel derived Pb<sub>1-x</sub>CaxTiO<sub>3</sub>. *Ferroelectrics* 2005; 324: 77-81. doi: 10.1080/00150190500324659
32. Chaudhari VA, Bichil GK. Sol-gel synthesis and characterization of lead titanate films. *Cogent Chemistry* 2015; 1: 1075323. doi: 10.1080/23312009.2015.1075323
33. Toyoda M, Hamaji Y, Tomono K. Fabrication of PbTiO<sub>3</sub> ceramic fibers by sol-gel processing. *Journal of Sol-Gel Science and Technology* 1997; 9: 71-84.
34. doi: 10.1023/A:1026464424392
35. Eichel R-A, Drahus MD, Jakes P, Erünal E, Erdem E et al. Defect structure and formation of defect complexes in Cu<sup>2+</sup>-modified metal oxides derived from a spin-Hamiltonian parameter analysis. *Molecular Physics* 2009; 107: 1981-1986. doi: 10.1080/00268970903084920
36. Abragam A, Bleaney B. *Electron paramagnetic resonance of transition ions*, Clarendon Press, London, 1970.
37. Weil JA, Bolton JR. *Electron paramagnetic resonance-elementary theory and practical applications*, 2nd ed., John Wiley & Sons, New Jersey, 2007.
38. Telser J. A perspective on applications of ligand-field analysis: inspiration from electron paramagnetic resonance spectroscopy of coordination complexes of transition metal ions. *Journal of the Brazilian Chemical Society* 2006; 17: 1501-1515.
39. doi: 10.1590/S0103-50532006000800005
40. Lou Y, Wang L, Zhang Y, Zhao Z, Zhang Z et al. The effects of Bi<sub>2</sub>O<sub>3</sub> on the CO oxidation over Co<sub>3</sub>O<sub>4</sub>. *Catalysis Today* 2011; 175: 610-614. doi: 10.1016/j.cattod.2011.03.064
41. Greenwood NN, Earnshaw A. *Chemistry of the elements*, 2nd ed., Butterworth-Heinemann, Oxford, 1997.
42. Roth WL. The magnetic structure of Co<sub>3</sub>O<sub>4</sub>. *Journal of Physical Chemistry of Solids* 1964; 25: 1-10. doi: 10.1016/0022-3697(64)90156-8
43. Gawali SR, Gandhi AC, Gaikwad SS, Pant J, Chan T-S et al. Role of cobalt cations in short range antiferromagnetic Co<sub>3</sub>O<sub>4</sub> nanoparticles: a thermal treatment approach to affecting phonon and magnetic properties. *Scientific Reports* 2018; 8: 249. doi: 10.1038/s41598-017-18563-9
44. Szafraniak-Wiza I, Hilczer B, Pietraszko A, Talik E. Phase formations during mechanochemical synthesis of PbTiO<sub>3</sub>. *Journal of Electroceramics* 2008; 20: 21-25. doi: 10.1007/s10832-007-9339-4
45. Burns G, Scott BA. Raman studies of underdamped soft modes in PbTiO<sub>3</sub>. *Physical Review Letters* 1970; 25: 167-170. doi: 10.1103/PhysRevLett.25.167
46. Meng JF, Katiyar RS, Zou GT. Grain size effect on ferroelectric phase transition in Pb<sub>1-x</sub>BaxTiO<sub>3</sub> ceramics. *Journal of Physics and Chemistry of Solids* 1998; 59: 1161-1167. doi: 10.1016/S0022-3697(97)00139-X
47. Hu Y, Gu H, Sun X, You Jing, and Wang J. Photoluminescence and raman scattering studies on PbTiO<sub>3</sub> nanowires fabricated by hydrothermal method at low temperature. *Applied Physics Letters* 2006; 88: 193120. doi: 10.1063/1.2203736
48. Fontana MD, Idrissi H, Kugel GE, Wojcik K. Raman spectrum in PbTiO<sub>3</sub> re-examined: dynamics of the soft phonon and the central peak. *Journal of Physics: Condensed Matter* 1991; 3: 8695-8705. doi: 10.1088/0953-8984/3/44/014
49. Bartaszyte A, Margueron S, Santiso J, Hlinka J, Simon E et al. Domain structure and Raman modes in PbTiO<sub>3</sub>. *Phase Transitions* 2011; 84: 509-520. doi: 10.1080/01411594.2011.552433
50. Ma W, Zhang M, Lu Z. A study of size effects in PbTiO<sub>3</sub> nanocrystals by raman spectroscopy. *Physica Status Solidi a* 1998; 166: 811-815. doi: 10.1002/(SICI)1521-396X(199804)166:2<811::AID-PSSA811>3.0.CO;2-X
51. Yahyaoui MM, Limame K, Sayouri S, Jaber B and Laanab L. Synthesis and structural studies of sol gel processed nanopowders of lead doped Y<sub>2</sub>Ti<sub>2</sub>O<sub>7</sub> pyrochlores. *Journal of Ceramic Processing Research* 2017; 18: 252-260.
52. Zhao Q, Liu Q, Zheng Y, Han R, Song C et al. Enhanced catalytic performance for volatile organic compound oxidation over in-situ growth of MnO<sub>x</sub> on Co<sub>3</sub>O<sub>4</sub> nanowire. *Chemosphere* 2020; 244: 125532. doi: 10.1016/j.chemosphere.2019.125532
53. Hsu M-C, Sun Y-M, Leu I-C, Hon M-H. Structural and electrical characterizations of PbTiO<sub>3</sub> thin films grown on LaNiO<sub>3</sub>-buffered Pt/Ti/SiO<sub>2</sub>/Si substrates by liquid phase deposition. *Journal of the Electrochemical Society* 2006; 153 (11): F260-F265. doi: 10.1149/1.2349279

54. Kwak JH, Han JK, Kang SW, Johnson TA, Bu SD. Dielectric relaxation properties of PbTiO<sub>3</sub>-multiwalled carbon nanotube composites prepared by a sol-gel process. *Ceramics International* 2016; 42 (7): 8165-8169. doi: 10.1016/j.ceramint.2016.02.023
55. Kumar NS, Suvarna KP, Naidu KCB. Sol-gel synthesized and microwave heated Pb<sub>0.8-y</sub>La<sub>y</sub>Co<sub>0.2</sub>TiO<sub>3</sub> (y = 0.2–0.8) nanoparticles: Structural, morphological and dielectric properties. *Ceramics International* 2018; 44 (15): 18189-18199. doi: 10.1016/J.CERAMINT.2018.07.027